Only typographical correction will be accepted at this stage. 09-17-93 14:07:56

Status of the development of rechargeable lithium cells

G. Halpert, S. Surampudi, D. Shen, C-K Huang, S. Narayanan, E. Vamos and D. Perrone

Jet Propulsion Laboratory, California Institute of Technology, Pasadena, CA 91109 (USA)

Abstract

The progress in the development of the ambient temperature lithium- titanium disulfide rechargeable cell under development at the Jet Propulsion Laboratory is described in this paper. Originally aimed at achieving a specific energy of 100 Wh/kg, 'AA' cells have demonstrated 125 Wh/kg at the C/3 discharge rate. The results of evaluating cell design parameters are discussed and cycling test data are also included in the paper. Safety-tests results at various overcharge and overdischarge conditions and rates proved to be uneventful. The test results of cell with built-in overcharge mechanism proved the concept was feasible. Replacing the lithium foil electrode with a Li_xC resulted in a capacity at 1 mA/cm^2 of 200 mAh/g and 235 mAh/g at 0.167 mA.

Introduction

Ambient temperature lithium- titanium disulfide (Ii- TiS_2) rechargeable cells have been under development at the Jet Propulsion Laboratory (J}'] .). T 'he, effort sponsor ccl by Code C at NASA Headquarters is aimed at high specific energy rechargeable cells that can reduce mass, and/or volume and or increase mission capability in planetary spacecraft applications. The need for a long cycle. life lithium rechargeable battery has also been a goal of this effort. The program goals were. 100 Wh/kg, 1 000 cycles at 50% depth-of-discharge at the C/5 rate, five. years of active storage life and safe under electrical abuse conditions.

The approach has tree.n to prepare materials, components and cells to gain an understanding of how the validations in design, composition and structure affect performance and life. During the development a number of cathode materials were studied in a comprehensive evaluation process before selecting titanium disulfide for its specific energy and cycle-life capability. More than 75 different ~~and~~ solvent combination electrolytes were subjected to complex impedance, microcalorimetry and electrochemical measurements before. selecting a solution of 2-methyltetrahydrofuran/ethylene carbonate/ 2-methylfuran (2-MeTHF/EC/2-MeF) containing 1.5 M of lithium hexafluoroarsenate (1 $LiAsF_6$). The initial evaluation cells were a)S0 mAh spiral-wound design. These were. scaled-up to 1 -Ab size spiral-wound cells. The volume of electrolyte was found to be essential to long life.

The objectives of this effort were to determine the effect of stack compression, over charge. protection and electrical abuse on the performance and safety of the Li-TiS_2 cell. Additionally, an alternate Li_xC electrode, prepared from commercial graphite, was evaluated as a replacement for lithium foil as the. anode.

0378-7753/93/$6.00 ©1993 - Elsevier Sequoia, All rights reserved

short

Elsevier Sequoia S. A. Box 564, 1001 Lausanne 1, Switzerland
Journal of Power Sources
AUTHOR QUERIES | EDITOR CORRECTION | MASTERCOPY Vol. No. P | pages
IN ALL CORRESPONDENCE CONCERNING THIS PAPER
Only typographical correction will be accepted at this stage.
09-17-93 14:07:56

Performance

Examples of the performance of these cells is given in Figs. 1 to 4. Figure 1 shows the voltage on charge (C/10) and discharge (C/5). Charge is terminated at 2.5 V and discharge at 1.7 V. The sloping voltage has the advantage of providing a measure of state-of-charge. Figure 2 provides a measure of the specific energy at various discharge rates. Note that the 1-Al) cell achieved a specific energy of greater than 125 Wh/Kg at rates as high as C/2. Figure 3 illustrates 965 cycles achieved at 50% depth-of-discharge (to 2.2 V) in a cell comprising the 2-MeTHF/EC/2-MeF/LiAsF$_6$ electrolyte and a cathode:anode ratio of 4:1. The cycle life at 100% depth-of-discharge (to 1.7 V) shown in Fig. 4 was 335 cycles. This is not significantly less than that achieved with commercial Ni-Cd cells.

Cell design parameters

The parameters addressed during the development process this year included: pack thightness, final selection of electrolyte composition, separator type, electrode

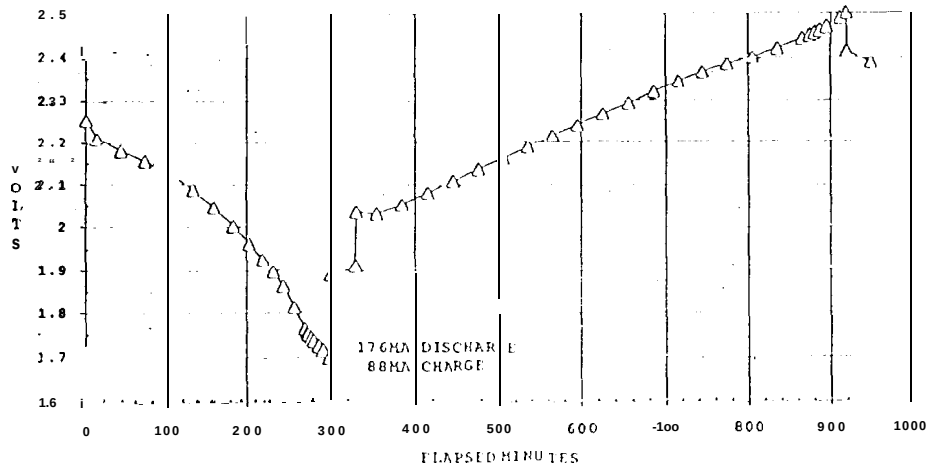

Fig. 1. Li-TiS$_2$ charge/discharge curve.

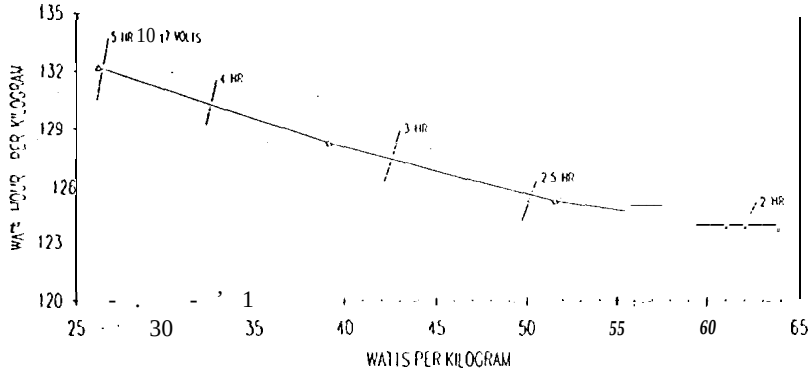

Fig. 2. Performance of a typical 1-Ah Li-TiS$_2$ cell.

Elsevier Sequoia S. A., Box 564, 1001 Lausanne 1, Switzerland
Journal of Power Sources
AUTHOR QUERIES | EDITOR CORRECTION | 1 MASTERCOPY Vol. No. pp. pages | IN ALL CORRESPONDENCE CONCERNING THIS PAPER REFER TO (without ELCOM) ELCOM3 POWER$1771
Only typographical correction will be accepted at this stage.
09-17-93 14:07:56

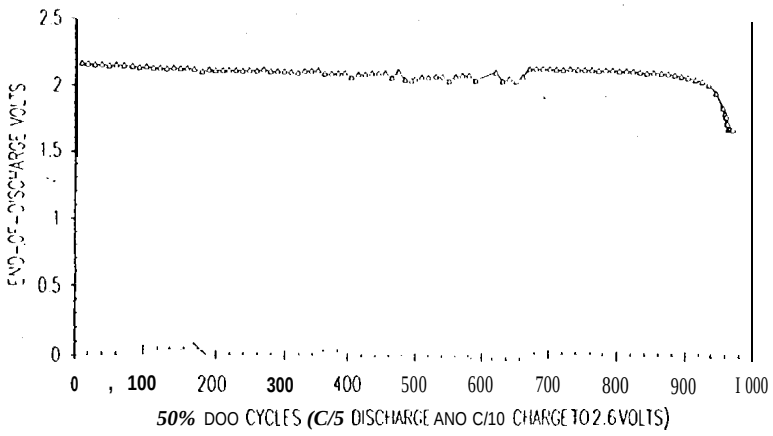

Fig. 3. Cycle life of a Li-TiS_2 ccl] at 50% depth-of-discharge.

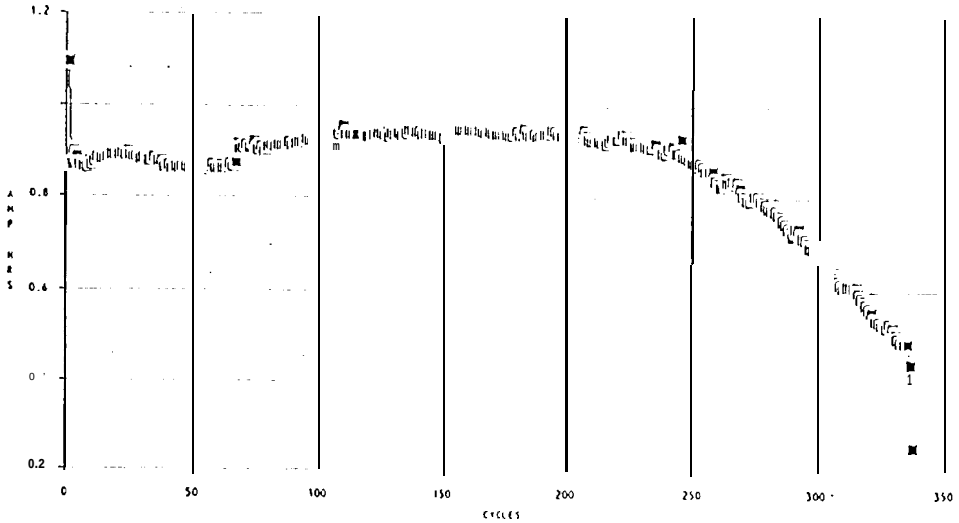

Fig. 4. Cycle life. of a Li-TiS_2 cell at 1 DO% depth-of-discharge.

capacity ratio and case polarity. More than 100 experimental 1-Ah spiral-wrapped cells wer c. assembled in house and 50 'AA' (1 Ah) cells were procure.d from EIC to deter mine t he effect of these parameters on t performance.

EdC laboratories Incorporated (1)

The effect of varying the pack tightness on end-of-discharge voltage is given in Fig. S. The pack was tightened using a 10 mil Teflon sheet wrapped around the spiral. The tight pack utilized two layers around the spiral, the medium one layer and the loose pack did not usc a Teflon layer. Although there is a significant difference in the early cycles, the performance appears to be similar after 2.50 cycles, probably bc.cause of the expansion of the cathode and film on the lithium foil. However, the. tight pack voltage was higher throughout and therefore was judged to be a superior configuration.

Elsevier Sequoia S. A., Box 564, 1001 Lausanne 1, Switzerland

Journal of Power Sources

IN ALL CORRESPONDENCE CONCERNING THIS PAPER REFER TO (without ELCOM)

AUTHOR QUERIES | EDITOR CORRECTION | MASTERCOPY Vol. No. pp. pages | ELCOM3 POWER$1771

Only typographical corrections will be accepted at this stage. 09-17-93 14:07:56

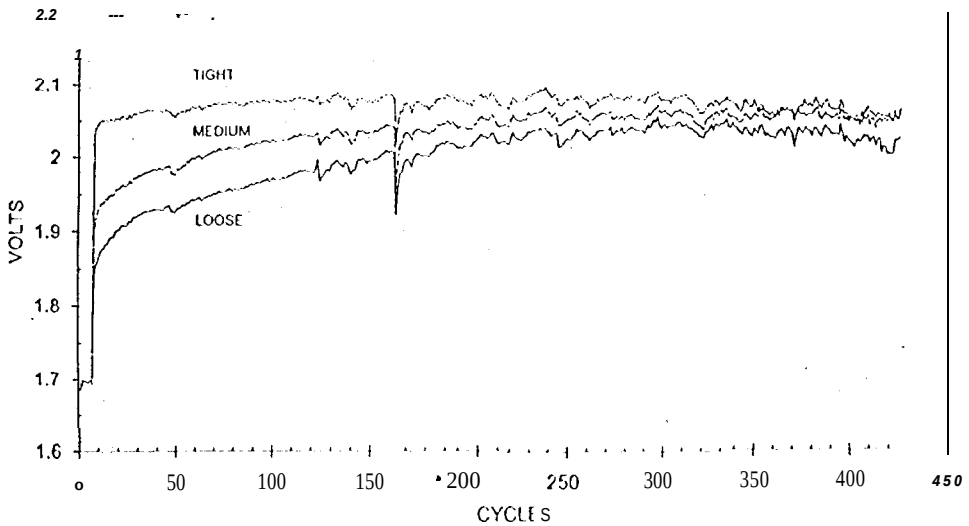

Fig. 5. Effect of pack tightness on end-of-discharge voltage.

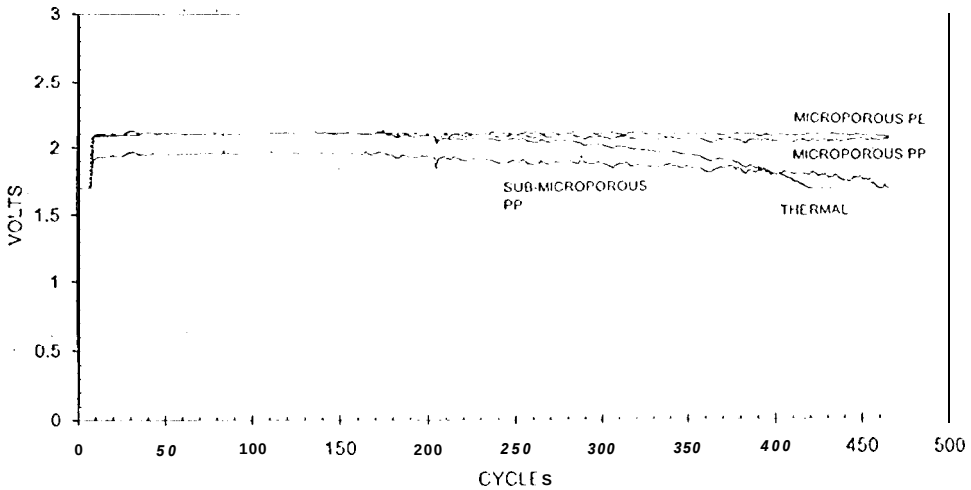

Fig. 6. Effect of separator on end-of-discharge voltage.

Results of the evaluation of four different separators is shown in Fig. 6. The Celgard microporous polyethylene and polypropylene appear to provide similar results. The microporous polypropylene was selected to minimize the lithium dendrite growth. The thermal separator, a wax-coated polypropylene material, was selected to evaluate the properties of a separator that would serve as a fuse and shut down the cell if the temperature became unsafe. These also provided more than 400 cycles at 50% depth-of-discharge.

The summary of the design parameter study, including work previously performed is given in Table 1. The anode:cathode ratio of 4:1 has been shown to provide consistent long-cycle-life cells. Three electrolytes including that described above have proven to

Elsevier Sequoia S. A., Box 564, 1001 Lausanne 1, Switzerland

Journal of Power Sources

AUTHOR	EDITOR	MASTERCOPY	pages
QUERIES	CORRECTION	Vol. No. pp.	

Only typographical correction will be accepted at this stage.

IN ALL CORRESPONDENCE CONCERNING THIS PAPER REFER TO (without ELCOM)

ELCOM3 POWER$1771

09-17-93 14:07:50

TABLE 1

Cell design parameters

Design parameters	Variations
Anode to cathode capacity ratio	4:1
Pack tightness	tight
Type of electrolyte	10% EC + 88% 2-MeTHF + 2% 2-MeF
Salt: 1.5 M $LiAsF_6$	THF + 2-MeTHF + 2% 2-MeF
	DIOX + 2-MeTHF + THF + 2% 2-MeF
Quantity of electrolyte	6 cm^3
Separator	microporous polypropylene
	microporous polyethylene
Binder concentration	1 wt.%
Case. polarity	floating or positive

EC: ethylene carbonate; 2-MeTHF: 2-methyltetrahydrofuran; 2-MeF: 2-methylfuran; THF: tetrahydrofuran; DIOX: Dioxolane.

capable of providing long life. Only 6 cm^3 of the electrolyte were found to be necessary. The optimum ethylene/propylene/diene terpolymer binder in the $LiTiS_2$ cathode was found to be 1 %. There was little difference in performance with a floating or case positive polarity.

Safety evaluation tests

Experimental and EIC 1-Ah cells were subjected to short circuit, overcharge, overdischarge, and combinations thereof. The results of the short-circuit test is given in Fig. 7. Peak current rose to 25 A within 2 min and then dropped to near zero current immediately after. The temperature followed the current, rising 10220 °F (102 °C), then tapering to 95 °F (33 °C) within 30 min. There were no ventings, explosions or other safety incidents during these tests. Table 2 provides a summary of the results of inadvertent electrical abuse tests which occurred during cell testing when a computer failed. Even after overcharging five times and overdischarging ten times the capacity after 200 to 500 cycles, the cells were intact and did not vent.

Overcharge protection studies

From an operational point of view, cells in a series string require overcharge protection to prevent a cell from being overcharged when degradation results in cell imbalance in the string. Ni–Cd cells utilize their inherent oxygen recombination capability to allow cells in a string to be balanced during overcharge. Lithium rechargeable cells do not inherently have this capability. Three additives were included in Li–TiS_2 cells to catalyze a shuttle reaction that could provide overcharge protection. Tetracyanoethylene, N-butylferrocene, suggested by EIC and JPL, tetramethylphenylenediamine were evaluated. Figure 8 shows the result of adding tetramethylphenylenediamine to a cell. The additive provided 10 to 15% capacity at 2.9 V thus protecting the cell during that period. Tetracyanoethylene did not provide adequate protection. N-butylferrocene from early measurements appears to be comparable to or better than tetramethylphenylenediamine.

Elsevier Sequoia S. A., Box 564, 1001 Lausanne 1, Switzerland
Journal of Power Sources
AUTHOR | EDITOR | MASTERCOPY
QUERIES | CORRECTION | Vol. No. pp. pages
Only typographical correction will be accepted at this stage.
IN ALL CORRESPONDENCE CONCERNING THIS PAPER REFER TO (without ELCOM)
ELCOM3 POWER$1771
09-17-93 14:07:56

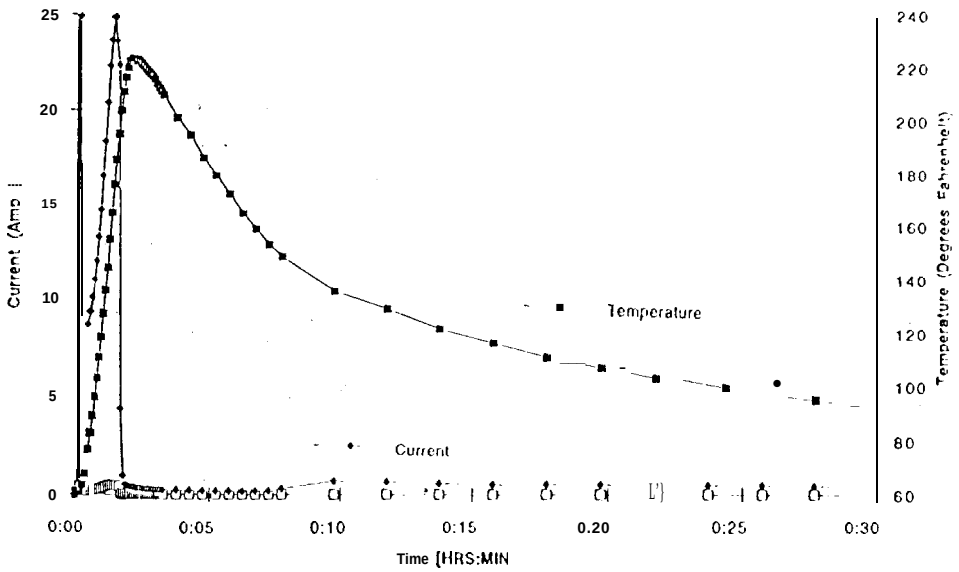

Fig. 7. Short circuit of a 1 Ah 'AA' Li-TiS_2 cell.

TABLE 2

Results of electrical abuse tests on 1 Li-TiS_2 cells

Cycle no.	Type of abuse	Rate	Abuse (%)	Event
200	overcharge	C/10	400	none
400	overcharge	C/10	500	none
550	overcharge	C/10	500	none
400	overdischarge	C/5	1000	none
500	overdischarge	C/5	1000	none

Lithium–carbon anodes

Replacement of lithium foil electrodes with an alternative lithium anode to enhance safety has been of interest. The performance targets for this material were 250 mAh/g and >2 mA/cm^2 with good mechanical stability. One of areas JPL's effort has centered on is the development of a lithium–carbon alloy (Li_xC). Several carbon materials, including pitch coke, petroleum coke, graphite fiber and graphite were evaluated as potential candidates. The rate capability of Li_xC using the graphite material is shown in Table 3. At 1 mA/cm^2 a capacity of 200 mAh/g was achieved. At the lower rates, higher capacities to 235 mAh/g were found. A discharge curve is given in Fig. 9. As expected, the voltage of this experimental cell was below the lithium foil electrode cells. The Li_xC electrode was only 72 mV below the lithium electrode potential at the start of the discharge and increased to 264 mV at the end of the discharge. Thus, it had a discharge curve comparable with that of the lithium foil cells.

[isov1oc Sequoia S. A., Box 564, 1001 Lausanne 1, Switzerland
Journal of Power Sources
IN ALL CORRESPONDENCE CONCERNING THIS PAPER REFER TO (without ELCOM)
AUTHOR | EDITOR | MASTERCOPY | pages
QUERIES | CORRECTION | Vol. No. pp.
ELCOM3 POWER$1771
Only typographical correction will be accepted at this stage.
09-17-93 14:38:25

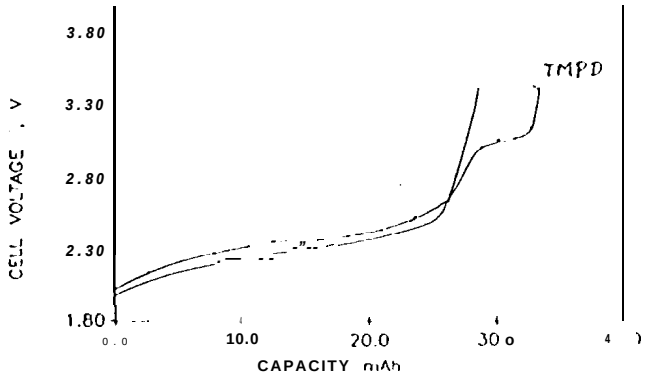

Fig. 8. Results of adding tetramethylphenylenediamine to a cell for overcharge protection; (i) 70-75% of theoretical capacity (stabilized in five cycles); (ii) overcharge performance; (iii) 25 cycles with stabilized capacity, compatible with the cell, and JO 15% overcharge protection at the normal charge rate.

'l'All] .E3

Rate capability of a Li_xC anode

Current (mA/cm²)	Capacity (mAh/g)
0.167	235
0.333	214
0.667	?08
1.000	?00

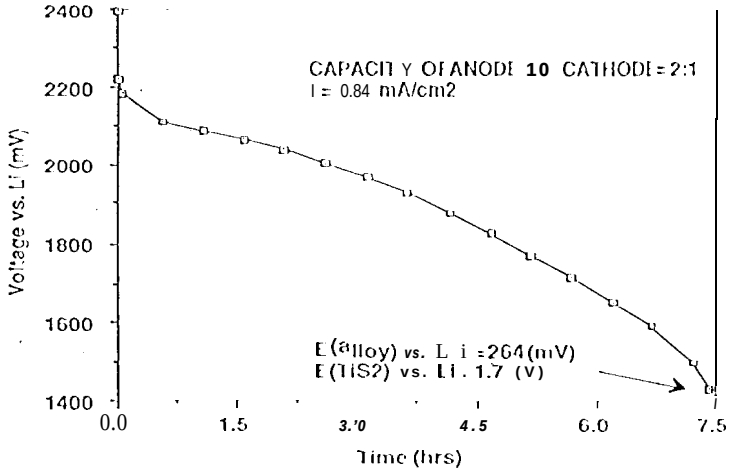

Fig. 9. 1 Discharge curve of a Li_xC-TiS_2 cell.

long

Elsevier Sequoia S. A., Box 564, 1001 Lausanne 1, Switzerland
Journal of Power Sources
IN ALL CORRESPONDENCE CONCERNING THIS PAPER REFER TO (without ELCOM)
AUTHOR QUERIES | EDITOR CORRECTION | MASTERCOPY Vol. No. pp. pages
ELCOM3 POWER$1771
Only typographical correction will be accepted at this stage.
09-17-93 14:38:25

Summary

Ambient temperature rechargeable Li-TiS_2 cells have demonstrated a capability of 125 Wh/kg at rates greater than C/2 and almost 1000 cycles at 50% depth-of-discharge. Design studies identified that a tight pack provided a more consistent and higher operating voltage. Microporous polyethylene or polypropylene were found to be suitable as separator material. The electrolyte and anode:cathode ratios among other parameters were also specified. Significant electrical abuse did not result in a venting or explosion. Overcharge protection was shown to be possible in these cells. A Li_6C alloy was found to be a suitable replacement for lithium foil with predictable reduction in specific energy for the. loss in lithium metal.

Acknowledgement

The work described herein was carried out at the Jet Propulsion Laboratory, California Institute of Technology, under a contract with the National Aeronautics and Space Administration (Code C).